




Radiation cross-linkable, halogen-free, flame retardant insulation and sheathing compound

<p>■ Compound class Insulation / sheathing</p>	<p>■ Compound category </p>	<p>■ Flame retardant ATH</p>
<p>■ Standards UL 3266</p>	<p>UL 3271</p>	
<p>■ Operating temperature [C°] -40 to 125</p>	<p>■ Oil resistance level ★</p>	

■ **Typical applications**
This compound is an ideal choice for the insulation of heat-resistant wires and cables for general applications in railway systems, nuclear power stations, engine compartments and other areas.









General Applications



Green Energy

■ **Features**

 Flame retardant	 Halogen-free	 Low smoke
 High temperature Resistant	 Flexible	 Flexible at low temperatures

PHYSICAL PROPERTIES

Physical properties	Unit	Typical value	Test method
Density*	g/cm ³	1.41	DIN EN ISO 1183-1A
Hardness*	Shore D	43	DIN ISO 7619-1
Melt Flow Index (160°C; 10kg)	g/10 min	7.0	DIN EN ISO 1133

MECHANICAL PROPERTIES

Before crosslinking**	Unit	Typical value	Test method
Tensile strength	N/mm ²	>8.5	IEC 60811-501
Elongation at break	%	>650	IEC 60811-501
After crosslinking ***	Unit	Typical value	Test method
Tensile strength (100-150kGy)	N/mm ²	17.0	IEC 60811-501
Elongation at break (100-150kGy)	%	350	IEC 60811-501
After ageing in air oven 168h at 158°C***	Unit	Typical value	Test method
Variation in tensile strength	%	10.0	IEC 60811-401
Variation in elongation at break	%	-2.0	IEC 60811-401

THERMAL PROPERTIES***

■ Low temperature tests	Unit	Typical value	Test method
Brittleness temperature (125kGy)	°C	-32,4	ASTM D 746-14
■ Hot set test at 200°C / 15min / 0,2MPa	Unit	Typical value	Test method
Elongation under load	%	20.0	IEC 60811-507
Residual elongation	%	10.0	IEC 60811-507

ELECTRICAL PROPERTIES*

■ Major electrical properties	Unit	Typical value	Test method
Volume resistivity	Ω cm	4.10¹²	ASTM D 257
Dielectric strength	kV/mm	25	ASTM D 149
Dielectric constant at 50Hz at 20°C	-	5	ASTM D 150
Dissipation factor at 50Hz at 20°C	-	0.025	ASTM D 150
Dielectric test (1.5 kV ; 1 minute)	-	Pass	UL

BURNING PROPERTIES*

■ Main burning properties	Unit	Typical value	Test method
LOI	%	31	ASTM D 2863 A
Halogen content	%	0	IEC 754-1
Temperature index	°C	225	ASTM D 2863 D
Toxicity index	-	2	EN 50305
■ Acid gas emission	Unit	Typical value	Test method
Corrosivity: pH (min.)	-	4.5	IEC 60754-2
Conductivity (max.)	μS/mm	2	IEC 60754-2

* pressed plaques

** extruded tapes

*** cross-linked plaques or tapes

PROCESSING GUIDE

■ **Screw configuration**

Good results have been achieved with ‘halogen-free’ screws, PVC screws and barrier type screws (BM) having high flights and a L/D-ratio > 24

■ **Screw cooling**

For high line speeds, cooling the screw to around 80°C could be effective, although this could lead to pulsation.

■ **Extrusion dies**


For pressure extrusion, normal dies are recommended.

■ **Die opening**

Die opening should be 1-5% below the required OD of the wire.
Little or no die land.

■ **Temperature profile extruder**

The profile shown below may vary slightly depending on extruder type, head design & output.

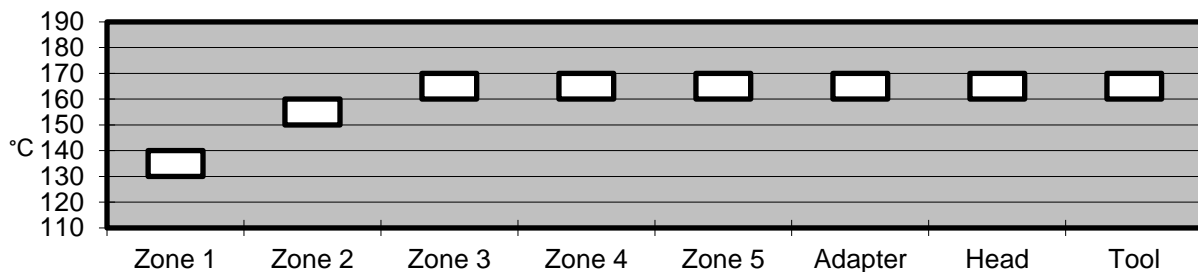

■ **Maximum mass temperature**

180°C

■ **Conductor pre-heating**

Pre-heating between 100°C-140°C to achieve maximum properties of elongation at break of the insulation.

■ **Wire/conductor**

Tin-coated

■ **Quenching**

After extrusion it should be possible to achieve an elongation at break of > 500%. By using wire pre-heating and or quenching in hot-water in the first cooling compartment, this may be optimized

■ **Drying**

Pre-dry at 50°C during 3 hrs, if necessary

■ **Recommended colour master batches**

Well dispersed EVA master batch 0,5-1,0%. For black jacket applications, UV resistance can be obtained by adding a higher level of master batch depending on requirements and type of carbon black master batch used.

CROSSLINKING INFORMATION

■ **Recommended radiation dose**

100-150 kGy

STORAGE INFORMATION

■ **Form & packaging**

Pellets in sizes 2.8mm
Moisture-resistant bags (25kg) & octabins (alu-innerliner, max. 1250kg)

■ **Shelf life**

1 year after production

Note: The information given in this datasheet is believed to be accurate and reliable. However, no warranty, express or implied, or guarantee is given as to the suitability, accuracy, reliability or completeness of the information. This information does not hold us liable for damages or penalties resulting from following our suggestions or recommendations.