
























Radiation cross-linkable, flame retardant compound for insulation and sheathing applications

<p>■ Compound class Insulation / sheathing</p> <p>■ Standards VG 95218, Part 24 (Type K), Part 25 (Type G) Part 27 (Type B), Part 28 (Type A and D)</p> <p>■ Operating temperature [C°] -50 to 150</p>	<p>■ Compound category</p> <div style="border: 1px solid black; background-color: orange; padding: 2px; width: 30px; margin: 0 auto;">RDX</div> <p>■ Oil resistance level ★★★★</p>	<p>■ Flame retardant Halogenated</p>																	
<p>■ Typical applications <i>System cabling for military vehicles, aerospace, sensor technology, engine & transformer construction, automotive motor compartments and industrial automation and process controls.</i></p>																			
																			
Marine, Aerospace, Defence	Automotive																		
<p>■ Features</p> <table border="0"> <tr> <td style="text-align: center;"></td> <td>Flame retardant</td> <td style="text-align: center;"></td> <td>Low smoke</td> <td style="text-align: center;"></td> <td>Oil resistant</td> </tr> <tr> <td style="text-align: center;"></td> <td>High temperature Resistant</td> <td style="text-align: center;"></td> <td>Abrasion resistant</td> <td style="text-align: center;"></td> <td>Flexible</td> </tr> <tr> <td style="text-align: center;"></td> <td>Flexible at low temperatures</td> <td colspan="3"></td> </tr> </table>				Flame retardant		Low smoke		Oil resistant		High temperature Resistant		Abrasion resistant		Flexible		Flexible at low temperatures			
	Flame retardant		Low smoke		Oil resistant														
	High temperature Resistant		Abrasion resistant		Flexible														
	Flexible at low temperatures																		

PHYSICAL PROPERTIES

Physical properties	Unit	Typical value	Test method
Density*	g/cm ³	1.3	DIN EN ISO 1183-1A
Hardness*	Shore D	28	DIN ISO 7619-1
Melt Flow Index (190°C; 2,16kg)	g/10 min	4.3	DIN EN ISO 1133
Abrasion*	-	Excellent	VG 95218/ 27

MECHANICAL PROPERTIES

Before crosslinking **	Unit	Typical value	Test method
Tensile strength	N/mm ²	>10	IEC 60811-501
Elongation at break	%	>600	IEC 60811-501

■ After crosslinking ***	Unit	Typical value	Test method
Tensile strength (130kGy)	N/mm ²	19	IEC 60811-501
Elongation at break (130kGy)	%	400	IEC 60811-501

THERMAL PROPERTIES***

■ Low temperature tests	Unit	Typical value	Test method
Elongation at break at -40°C	%	>150	IEC 60811-505
Elongation at break at -50°C	%	>30	IEC 60811-505
■ Hot set test at 200°C / 15min / 0,2MPa	Unit	Typical value	Test method
Elongation under load	%	25	IEC 60811-507
Residual elongation	%	10	IEC 60811-507

ELECTRICAL PROPERTIES*

■ Major electrical properties	Unit	Typical value	Test method
Volume resistivity	Ω cm	10¹³	ASTM D 257
Dielectric strength	kV/mm	20	ASTM D 2671
Dielectric constant at 50Hz	-	4.8	ASTM D 150

BURNING PROPERTIES*

■ Main burning properties	Unit	Typical value	Test method
LOI	%	28	ASTM D 2863 A
Flammability	-	Pass	UL VW-1

* pressed plaques

** extruded tapes

*** cross-linked plaques or tapes

Processing Guide

■ **Screw configuration**


Barrier type screw (BM) having high flights and a L/D-ratio > 24:1

■ **Extrusion dies**

With both pressure tooling and tube extrusion, good results have been achieved

■ **Temperature profile extruder**

The profile shown below may vary slightly depending on extruder type, head design & output.

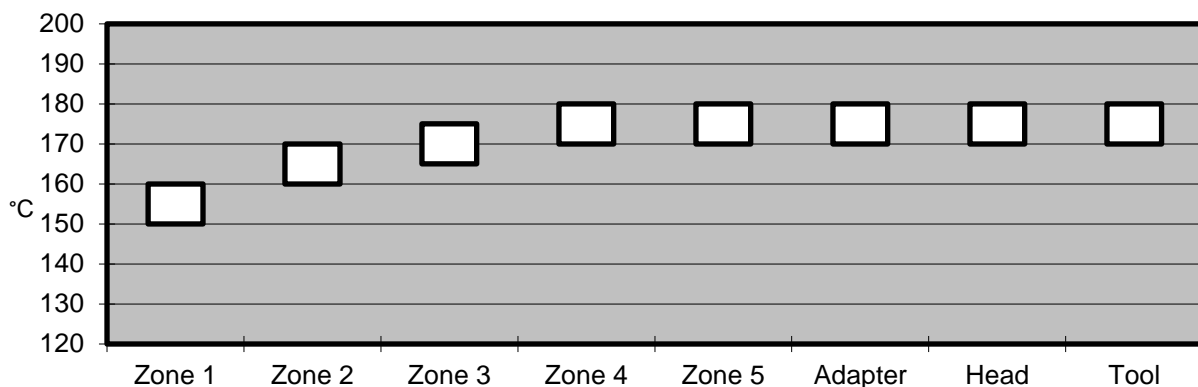

■ **Maximum mass temperature**

190°C

■ **Wire/conductor**

For insulation applications a tin coated conductor is recommended

■ **Drying**

Pre-dry at 50°C during 3 hrs

■ **Recommended colour master batches**

We recommend to use high quality, well dispersed EVA master batch 0,5-1,0%. For black jacket applications, UV resistance can be obtained by adding a higher level of master batch depending on requirements and type of carbon black master batch used.

Crosslinking information

■ **Recommended radiation dose**

120-150kGy

Storage information

■ **Form & packaging**

Pellets in sizes 2.8mm
Moisture-resistant bags (25kg) & octabins (alu-innerliner, max. 1250kg)

■ **Shelf life**

1 year after production

Note: The information given in this datasheet is believed to be accurate and reliable. However, no warranty, express or implied, or guarantee is given as to the suitability, accuracy, reliability or completeness of the information. This information does not hold us liable for damages or penalties resulting from following our suggestions or recommendations.