








## Halogen-free, radiation cross-linkable, flame retardant sheathing compound

<p>■ <b>Compound class</b> Sheathing</p>	<p>■ <b>Compound category</b> </p>	<p>■ <b>Flame retardant</b> ATH</p>
<p>■ <b>Operating temperature [C°]</b> -40 to 145</p>	<p>■ <b>Oil resistance level</b> ★★★</p>	
<p>■ <b>Typical applications</b> <i>Halogen-free, low smoke, highly oil and extra fuel resistant radiation cross-linkable, max. operating temperature 145°C, flame retardant compound of low and medium voltage cables for General Installation applications.</i></p>		
		
<p>General Applications</p>		
<p>■ <b>Features</b></p>		
 Flame retardant	 Halogen-free	 Low smoke
 Oil resistant	 High temperature resistant	

## PHYSICAL PROPERTIES

Physical properties	Unit	Typical value	Test method
Density*	g/cm <sup>3</sup>	<b>1,53</b>	DIN EN ISO 1183-1A
Hardness*	Shore D	<b>45</b>	DIN ISO 7619-1
Melt Flow Index (150°C; 21,6kg)	g/10 min	<b>15</b>	DIN EN ISO 1133

## MECHANICAL PROPERTIES

Before crosslinking **	Unit	Typical value	Test method
Tensile strength	N/mm <sup>2</sup>	<b>≥ 10,0</b>	IEC 60811-501
Elongation at break	%	<b>≥ 220</b>	IEC 60811-501
After crosslinking ***	Unit	Typical value	Test method
Tensile strength (150kGy)	N/mm <sup>2</sup>	<b>≥ 13,5</b>	IEC 60811-501
Elongation at break (150kGy)	%	<b>≥ 175</b>	IEC 60811-501
After ageing in air oven 3000h at 145°C ***	Unit	Typical value	Test method
Variation in tensile strength	%	<b>-1,5</b>	IEC 60811-401
Variation in elongation at break	%	<b>-26,3</b>	IEC 60811-401

## THERMAL PROPERTIES \*\*\*

■ Hot set test at 200°C / 15min / 0,2MPa	Unit	Typical value	Test method
Elongation under load	%	<b>15</b>	IEC 60811-507
Residual elongation	%	<b>5</b>	IEC 60811-507

## RESISTANCE \*\*\*

■ Fluid IRM 902 24h at 100°C (150kGy)	Unit	Typical value	Test method
Variation in tensile strength	%	<b>-28,7</b>	IEC 60811-404
Variation in elongation at break	%	<b>+10,4</b>	IEC 60811-404
Variation in weight	%	<b>+44,1</b>	IEC 60811-404

## BURNING PROPERTIES \*

■ Main burning properties	Unit	Typical value	Test method
LOI	%	<b>34</b>	ASTM D 2863 A

## ELECTRICAL PROPERTIES\*

■ Major electrical properties	Unit	Typical value	Test method
Volume resistivity (500 V, 23°C)	Ω cm	<b>3,1*10<sup>14</sup></b>	VDE 0303-30
Volume resistivity (500 V, 90°C)	Ω cm	<b>1,7*10<sup>12</sup></b>	VDE 0303-30

\* pressed plaques, 155°C / 5 min.

\*\* extruded tapes

\*\*\* cross-linked plaques / tapes

## PROCESSING GUIDE

■ **Extruder Type**

Standard extruders for elastomeric or thermoplastic processing.

■ **Screw configuration**


Low compression screw with L/D of 20 to 25 and compression ratio of 1:1.2

■ **Tooling**

For insulation pressure tools, for jacketing tube tools are recommended. Note: Pressure Tooling may have an effect on low temperature flexibility.

■ **Temperature profile extruder**

The profile shown below may vary slightly depending on extruder type, head design & output.

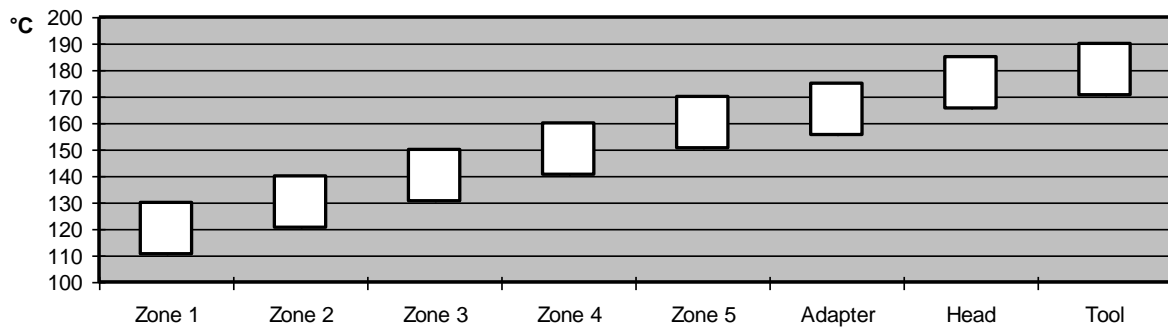

■ **Maximum mass temperature**

170-180°C

■ **Drying**

Not necessary if the compound has been stored in original packing under cool (max. 30°C) and dry conditions. Mecoline compounds used from open packing require pre-drying during 4–6 hours at 60–70°C.

## CROSS-LINKING INFORMATION

■ **Recommended radiation dose**

150 kGy

## STORAGE INFORMATION

■ **Form & packaging**

Pellets in sizes 2.8mm & 5.5mm  
Moisture-resistant bags (25kg) & octabins (alu-innerliner, max. 1250kg)

■ **Shelf life**

1 year after date of manufacturing

Note: The information given in this datasheet is believed to be accurate and reliable. However, no warranty, express or implied, or guarantee is given as to the suitability, accuracy, reliability or completeness of the information. This information does not hold us liable for damages or penalties resulting from following our suggestions or recommendations.